

UNCLASSIFIED

AD NUMBER
AD848202
NEW LIMITATION CHANGE
TO Approved for public release, distribution unlimited
FROM Distribution authorized to U.S. Gov't. agencies only; Administrative/Operational Use; 11 JAN 1968. Other requests shall be referred to Naval Fleet Missile Systems Analysis and Evaluation Group, Attn: IDEP Office, code ELD, Corana, CA 91728.
AUTHORITY
usnwc ltr, 30 aug 1974

THIS PAGE IS UNCLASSIFIED

THE ATTACHED INFORMATION IS SUBMITTED AT U.S. GOVERNMENT REQUEST, FOR DISTRIBUTION AT THE DISCRETION OF THE RECEIVING GOVERNMENT AGENCY. IT MAY BE CALLED "PRELIMINARY" OR "DRAFT," BUT EVEN IF "FINAL," IT MAY BE CHANGED WITHOUT ADVISING ALL PRIOR RECIPIENTS. SUBMITTAL IMPLIES THE ORIGINATOR'S PERMISSION FOR RECIPIENTS TO UTILIZE THIS DOCUMENT FOR PARTS PROCUREMENT OR OTHER ACTIONS, BUT ENTIRELY AT THE RECIPIENT'S OWN RISK.

IDEP FORM 12-11-62



Q4318

SPECIFICATION

1 of 1

1. COMPONENT/PART NAME PER GENERIC CODE PROPULSION PARTS & MATERIALS, SOLID FUEL ENGINES, PROPELLANTS	2. PROGRAM OR WEAPON SYSTEM MULTIPLE	3. DATE OF: DAY MO YR		
		ISSUE	11	1 68
		REVISION		
4. ORIGINATOR'S SPECIFICATION TITLE PURCHASE DESCRIPTION, COPOLYMER, VINYLIDENE DIFLUORIDE AND HEXAFLUOROPROPYLENE	5. ORIGINATOR'S SPEC. NO. WS 7682			
	6. SPECIFICATION IS: <input type="checkbox"/> DRAFT <input type="checkbox"/> PRELIMINARY <input checked="" type="checkbox"/> FINAL			
7. THIS SPECIFICATION COMPLEMENTS REPORT NO:				

8. TYPE OF SPECIFICATION

- | | |
|---|--|
| <input checked="" type="checkbox"/> (A) GENERAL PRODUCT REQUIREMENTS FOR A FAMILY OF PARTS - PROCUREMENT DOCUMENT
<input type="checkbox"/> (B) INDIVIDUAL DETAIL PARTS DOCUMENT; STDS BOOK PAGES - FOR PROCUREMENT
<input type="checkbox"/> (C) DETAIL INSPECTION, PROCESS CONTROL, AND/OR TEST PROCEDURES FOR SPECIFIC PARTS
<input type="checkbox"/> (D) PROCESS (PAINTING, WELDING, FINISHING, HEAT TREATING ETC.) APPLICABLE TO MANY PARTS | <input type="checkbox"/> (E) SPEC. FOR PERFORMANCE, RELIABILITY, AND/OR ENVIRONMENT FOR ASSEMBLIES, EQUIPMENTS, SUBSYSTEMS AND SYSTEMS
<input type="checkbox"/> (F) PERFORMANCE AND APPLICATION DATA FOR DESIGN ENG. USE ON PARTS - NOT FOR PROCUREMENT
<input type="checkbox"/> (G) OTHER (DETAIL IN 10.) |
|---|--|

NOTE: WHEN MULTIPLE FUNCTIONS ARE COMBINED IN ONE DOCUMENT, CHECK ALL APPLICABLE SQUARES.

9. APPLICABLE REFERENCED SPECIFICATIONS EXCEPT MIL-SPECS, STDS, OR OTHER UNIVERSALLY AVAILABLE DOCUMENTS.	ENCL.	AVAIL. ON REQ.	NOT AVAIL.	PREVIOUSLY SUBMITTED AND FILED AS IDEP REPORT OR SPEC. NUMBER

10. ADDITIONAL DESCRIPTION OF IMPORTANT DOCUMENT CONTENTS, SIGNIFICANT FEATURES, OR SPECIAL PURPOSE, NOT COVERED BY "TITLE":

STATEMENT #3 UNCLASSIFIED

Each transmittal of this document outside the agencies of the U.S. Government must have prior approval of *Officer in Charge (Code E6)*
US Naval Fleet Missile Systems Analysis & Evaluation Group; attn: Idep Office Corona Calif 91728

DDC
FEB 26 1969

11. SIGNED <i>M. S. L.</i>	12. CONTRACTOR NWC/CL	SUBCONTRACTOR
-------------------------------	--------------------------	---------------

13. SPEC. NO. 565.70.00.00-X7-17 5

REPRODUCTION OR DISPLAY OF THIS MATERIAL FOR SALES OR PUBLICITY PURPOSES IS PROHIBITED

13

76

13 1

AD848202

20994

NOTICES PAGE

FOREIGN NATION RELEASE

This information is furnished upon the condition that it will not be released to another Nation without specific authority of the cognizant agency (Military or NASA) of the United States Government, and that the information be provided substantially the same degree of protection afforded it by the Department of Defense of the United States.

DISCLAIMER OF LIABILITY FROM ACT OF TRANSMITTAL

When Government drawings, specifications, or other data are used for any purpose other than in connection with a definitely related Government procurement operation, the United States Government thereby incurs no responsibility nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specification, or other data, is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use, or sell any patented invention that may in any way be related thereto.

Any information disseminated by the Data Distribution Centers of the Interagency Data Exchange Program is intended to promote test data utilization in the National interest among groups engaged in Ballistic Missile, Space Vehicle and related programs.

Dissemination of said information does not imply verification or endorsement of the information. The originator, in submitting the material is acting in accordance with the requirements of his contract, and neither the originator nor the disseminator assumes any liability to parties adopting any product, process or practice based upon the usage of the information. Its presenting the success of failure of one (or several) part number(s), model(s), lot(s) under specific environment and output requirements, does not imply that other products not herein reported on are either inferior or superior.

OMISSION OF CHARGES FOR FOLLOW-ON ACTIONS

Any compliance by the report originator with requests from recipients for more detailed information in IDEP reports originated under Government contracts will be considered within the scope of present contractual obligations. Compliance with such requests will be at the discretion of the report originator and will be performed without cost or obligation to the requester unless otherwise negotiated in advance.

REPRODUCTION OF THIS REPORT

Reproduction or duplication of any portion of this report is expressly forbidden, except by those contractors receiving it directly from the Data Centers or originator, for their internal use or the use of their subcontractors. Reproduction or display of all or any portion of this material for any sales, advertising or publicity purposes is prohibited.

Code Ident
10001

WS 7682

NAVAL ORDNANCE SYSTEMS COMMAND


DEPARTMENT OF THE NAVY

PURCHASE DESCRIPTION

COPOLYMER, VINYLIDENE DIFLUORIDE AND

HEXAFLUOROPROPYLENE

Approved:


By direction 11 JAN 68

RECORD OF REVISIONS		
Revision Letter	Date	Changes

This document consists of pages i to ii and
1 to 10 inclusive.

FSC 6810

11ND-NOTS-4120/11(8-65)

Code Ident
10001

WS 7682

NAVAL ORDNANCE SYSTEMS COMMAND

DEPARTMENT OF THE NAVY

PURCHASE DESCRIPTION

COPOLYMER, VINYLIDENE DIFLUORIDE AND

HEXAFLUOROPROPYLENE

1. SCOPE.

1.1 This purchase description covers one type of soluble fluoroelastomer (SFE) used as a high density binder material.

2. APPLICABLE DOCUMENTS.

2.1 The following documents of the issue in effect on date of invitation for bids or request for proposal form a part of this document to the extent specified herein.

STANDARDS

Military

MIL-STD-129

Marking for Shipment and Storage.

MIL-STD-414

Sampling Procedures and Tables for Inspection by Attributes.

(Copies of specifications, standards, drawings, and publications required by suppliers in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

FSC 6810

3. REQUIREMENTS.

3.1 Product characteristics and performance. The copolymer is a product prepared by reacting vinylidene 1,1-difluoride and hexafluoropropylene. The presence of small amounts (less than 1 percent) of polymerization catalysts, coagulants, antioxidants or curing terminal groups may be acceptable. When tested in accordance with section 4, the binder material shall meet the following product characteristics and performance.

3.1.1 Chemical and physical properties. Chemical and physical properties of the binder material shall be in accordance with Table I.

Table I. Chemical and Physical Properties

Characteristic	Requirement	
	Min	Max
Vinylidene difluoride, % by weight	55	63
Volatile material, %	---	0.30
Insolubles in acetone, %	---	0.50
Inherent viscosity at 30°C	0.65	1.15

3.2 Workmanship. The binder material shall be made using good workmanship, and shall be a product free from foreign materials. It shall be uniform in quality and shall be manufactured in accordance with standard manufacturing procedures of the industry.

4. QUALITY ASSURANCE PROVISIONS.

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified, the supplier may utilize his own facilities or any commercial laboratory acceptable to the Government. The Government reserves the right to perform any of the inspections set forth in this document where such inspections are deemed necessary to assure that supplies and services conform to prescribed requirements.

4.2 Lot. A lot shall consist of binder material produced by one manufacturer in one continuous operation employing not more than one lot of each ingredient with no change in formulation or process. If manufacture is by batch process, batches may be combined to form a lot provided that not more than one lot of each ingredient is used. A batch shall be as defined in 6.3.

4.3 Sampling. Sampling for quality conformance tests shall be in accordance with MIL-STD-414, Standard Deviation Method, Variability Unknown, Acceptable Quality Level of 1.0 percent defective.

4.4 Quality conformance tests. The following test procedures shall be used to determine that the requirements of this document have been met. Any proposed change in test methods or equipment shall necessitate, before adoption, prior approval of the procuring activity. In case of dispute between the results obtained using the methods and equipment specified herein and any proposed methods and equipment, the results obtained from what is specified herein shall prevail.

4.4.1 Vinylidene difluoride.

4.4.1.1 Apparatus. Infrared spectrophotometer, covering a minimum range of from 5 (2000 cm^{-1}) to 10 (1000 cm^{-1}) microns, and set for maximum efficiency for this analysis.

4.4.1.2 Sample preparation.

- (a) Place a 0.7 \pm 0.1 gram (gm) sample into a small bottle (screw cap with aluminum foil liner).
- (b) Add 10 milliliters (ml) of acetone to the clean sample bottle containing the sample and a small Teflon coated stirring bar.
- (c) After screwing the cap in place, seal with masking tape.
- (d) Place the bottle on a magnetic stirrer and allow to stir until completely dissolved.

4.4.1.3 Procedure.

- (a) Let the dissolved sample settle (from 15 to 30 minutes) before the SFE solution is placed on the salt window (a sodium chloride window is satisfactory).

NOTE. Approximately two to three drops of the clear liquid from an eyedropper on an indented salt window will give a workable IR curve. After evaporation of the acetone, the film should give an absorbance between 0.6 and 0.9 at the 1400 cm^{-1} band to allow sufficiently accurate measurements to be made. If not, start again with a freshly prepared film.

- (b) Scan the film on the salt plate from approximately 2000 cm^{-1} to 1000 cm^{-1} .
- (c) Make certain that all the acetone has been removed from the film by checking the 1720 cm^{-1} region for an absorption band. If one is present, further drying is necessary.
- (d) Determine the wave numbers of minimum absorbance at approximately 1425 cm^{-1} and 1335 cm^{-1} and draw tangent line "ac" (see Figure 1). Determine wave numbers of maximum absorbances at 1405 cm^{-1} and 1355 cm^{-1} and draw lines tangent at "d" and "e" and normal to the absorbance scale. Draw a line from tangent point "d" perpendicular to the wave number scale intersecting line "ac" at "x" and another line from tangent point "e" perpendicular to the wave number scale intersecting line "ac" at "y".
- (e) Determine the absorbance differences: $d - x$ and $e - y$.
- (f) Calculate the absorbance ratio $\frac{d - x}{e - y}$.

Percent VF_2 is read from the calibration curve (see Figure 2).²

4.1.1.4 Acceptance criteria. For the lot represented to pass the vinylidene difluoride test, the result obtained shall be within the range given in Table I.

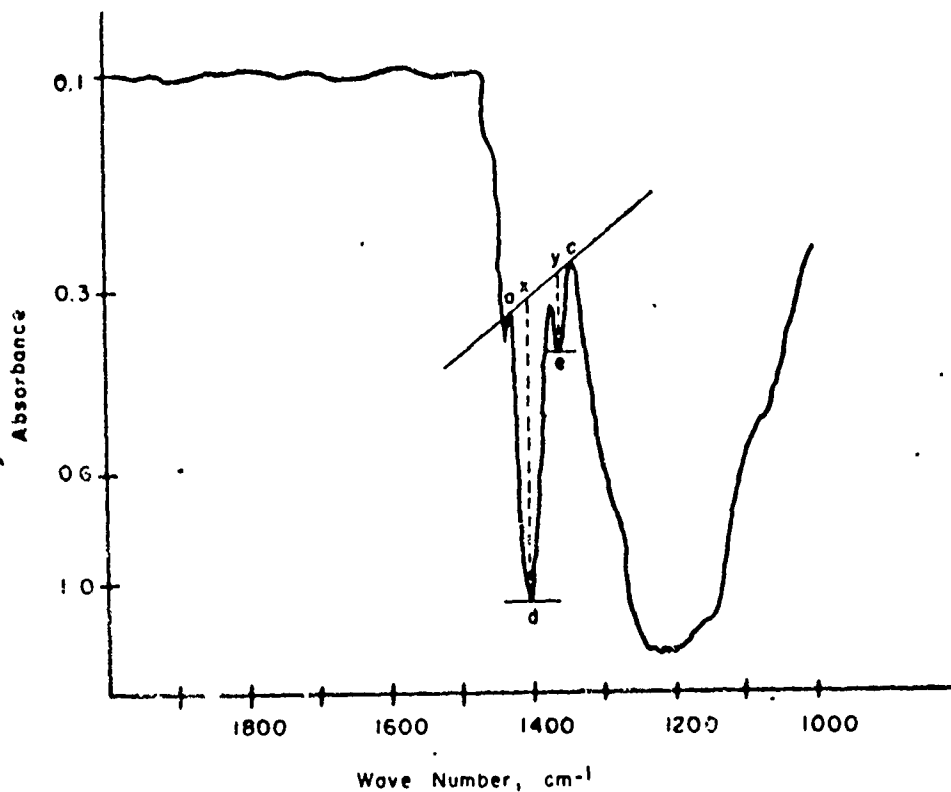


Figure 1

4.4.2 Volatile material. Volatile material shall be determined by oven drying at 204 ± 4 degrees centigrade ($^{\circ}\text{C}$) as follows: Prepare the sample by cutting small pieces 0.010 to 0.020 inch in thickness. Store in a glass stoppered bottle until ready for use. Clean and dry an aluminum pan at 204°C . Cool in a desiccator and weigh. Add approximately 15 gm of the sliced copolymer and reweigh. Place the pan and sample in the 204°C oven for 120 ± 1 minute. Cool in a desiccator to room temperature, then reweigh. Calculate the content of volatiles as follows:

$$\text{Volatiles, percent} = \frac{W_o - W_d}{W_o - W} \times 100$$

Where: W_o = weight of pan and original sample, gm

W_d = weight of pan and dried sample, gm

W = weight of dried and cooled pan, gm

4.4.2.1 Acceptance criteria. For the lot represented to pass the volatile-material test, the value obtained shall be no more than that given in Table I.

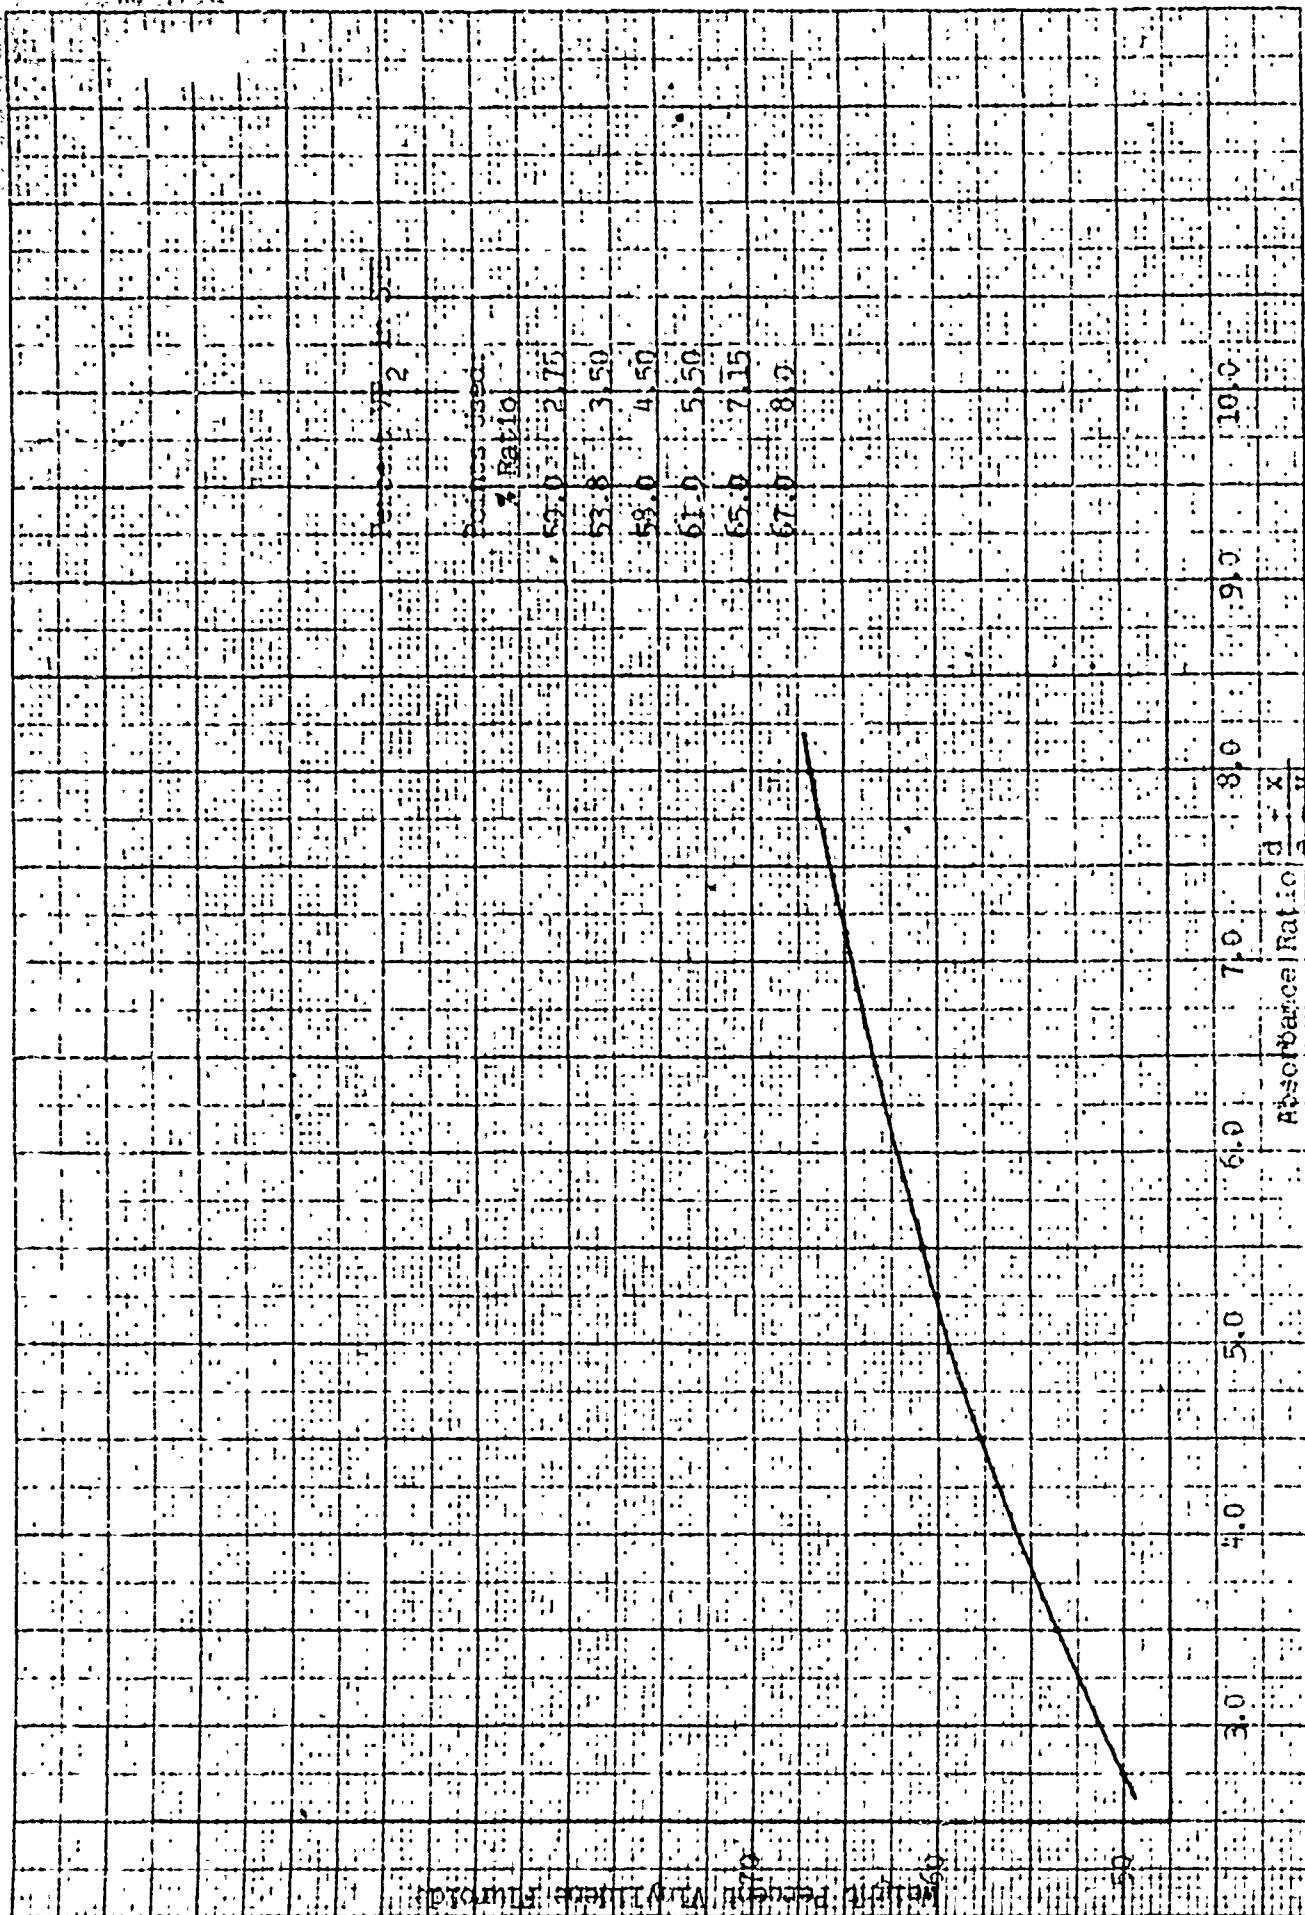


Figure 2. Calibration Curve for 4.4.1.3(f).

4.4.3 Insolubles in acetone. Solubility in acetone shall be determined by the following procedure. Place 10 gm of the SFE (weighed to the nearest 0.001 gm) into a clean, dry, 250 ml beaker and add 150 ml of reagent-grade acetone. Cover with aluminum foil and permit the SFE to soften for about 1 hour. Then stir until dissolved (about 1 hour). Let stand, covered, until insolubles settle (overnight) to aid filtration. Pack a GF/C glass filtering paper¹ wet with acetone over the fritted glass bottom of a 30 ml coarse filtering crucible.

Dry at 80°C, cool in desiccator, and weigh. Filter the SFE solution through the crucible. Police the beaker and transfer all residue to the crucible with a jet of acetone from a wash bottle. Wash all soluble material through the crucible with acetone. Use vacuum as needed, but do not let the frit become dry until the washing is complete. Dry in a well ventilated oven at 80°C for 30 minutes, cool in a desiccator, and weigh. Calculate the acetone insolubles as follows:

$$\text{Acetone insolubles, percent} = \frac{100 (R - P)}{W}$$

Where: R = weight of prepared crucible and residue, gm

P = weight of prepared crucible, gm

W = weight of sample, gm

4.4.3.1 Acceptance criteria. For the lot represented to pass the insolubles-in-acetone test, the result obtained shall be no more than that given in Table I.

4.4.4 Viscosity, inherent. Inherent viscosity shall be determined on a dilute solution of the copolymer SFE as follows:

Weigh 0.100 ±0.001 gm of copolymer with an accuracy of ±0.0002 gm and place in a 250 ml glass stoppered Erlenmeyer flask. Add, by pipet, 100 ml of solvent prepared by mixing 20 volumes of tetrahydrofuran with 3 volumes of dimethylformamide. Dissolve by shaking mechanically.

CAUTION

Avoid contact and fumes from these flammable solvents. Use in well ventilated hood.

¹Whatman GF/C glass fiber filters from Braun Corporation, 1363 South Bonnie Beach Place, Los Angeles, California 90023 proved satisfactory.

WS 7682

Filter the solution with the aid of a slight vacuum and centrifuge the filtrate in a Goetz tube for 30 minutes at 750 revolutions per minute. Transfer, by pipet, 10 ml of the gel-free and residue-free solution to a weighed 28 x 59 millimeter (mm) flat weighing bottle and evaporate the solvent gently in a warm vacuum oven. Weigh the bottle and residue to the nearest 0.0003 gm. Calculate the concentration of the solution as follows:

$$c = 10(W_2 - W_1)$$

Where: c = concentration of SFE, gm/100 ml

W_2 = weight of weighing bottle and dried copolymer, gm

W_1 = weight of empty weighing bottle, gm

Suspend a clean and dry Ostwald-Fenske viscometer tube, number 50 series, in a constant temperature water bath at $30 \pm 0.03^\circ\text{C}$. Pipette 10.0 ml of the mixed solvent to the large bulb and allow 10 minutes for temperature equalization. Calibrate the tube by drawing up the solvent, releasing, and determining the flow time for the meniscus to pass the two marks. Record the reading to the nearest 0.1 second. Drain and dry the tube. Determine the flow time for the copolymer SFE solution at $30 \pm 0.03^\circ\text{C}$ in the same manner. Calculate the relative viscosity of the solution as follows:

$$r = t/t_0$$

Where: r = relative viscosity, dimensionless ratio

t = flow time for sample solution, seconds

t_0 = flow time for mixed solvent, seconds

Calculate the inherent viscosity of the solution as follows:

$$\text{inh} = \frac{2.303 \log r}{c}$$

Where: inh = inherent viscosity number

r = relative viscosity

c = copolymer concentration, gm/100 ml

4.4.4.1 Acceptance criteria. For the lot represented to pass the inherent-viscosity test, the value obtained shall be within the range given in Table I.

4.5 Packaging, packing, and marking. Determine that packaging, packing, and marking conforms to section 5 of this document.

5. PREPARATION FOR DELIVERY.

5.1 Preservation and packaging.

5.1.1 Level A. Not applicable.

5.1.2 Level B. Not applicable.

5.1.3 Level C. The material shall be packaged in uniform quantities in sealed polyethylene bags or liners.

5.2 Packing.

5.2.1 Level A. Not applicable.

5.2.2 Level B. Not applicable.

5.2.3 Level C. Each individual package shall be packed in a fiber-board drum. The net weight of SFE shall be 50 or 100 pounds. The containers shall be acceptable to the carrier for safe delivery.

5.3 Marking.

5.3.1 Special marking. Each individual shipping container shall be marked to indicate the number of the batch or lot, whichever is the smaller, and the container number.

5.3.2 Normal marking. Shipping containers shall be marked in accordance with the requirements of MIL-STD-129.

6. NOTES.

6.1 Intended use. Lacquers made from this SFE are intended for use as binder material for pyrotechnics, propellants, and explosives.

WS 7682

6.2 Ordering data. Procurement documents should specify the following:

- (a) Title, number, and date of this document.
- (b) Material form (crumb or slab) desired.

6.3 Batch. A batch is defined as that material which has been subjected to one or more chemical or physical processes (or combinations thereof) intended to produce a desired product having substantially uniform characteristics.

6.4 Chemical composition. The copolymer is the product prepared by reacting vinylidene 1,1-difluoride with hexafluoropropylene. This should not be interpreted as preventing the addition of less than 1 percent of suitable modifiers in the polymerization mix for the addition of terminal or intermediate reactive groups to the polymer chain in order to produce a curable product, or to promote adhesion to recommended materials so long as all other specified performance criteria are met by the final product during testing. The presence of small amounts of polymerization catalysts, coagulants, antioxidants or curing terminal groups may be acceptable.

Custodian:
NAVORD ORD9343

Preparing Activity:
NAVWPNSCEN/China Lake, California